arXiv:cond-mat/0407557v2 [cond-mat.str-el] 7 Dec 2005

Jahn-Teller Coupled Charge Density Wave in A Two Orbital Double Exchange System

Manidipa Mitra*

S. N. Bose National Centre for Basic Sciences, JD Block,

Sector III, Salt Lake City, Kolkata - 700 098, India

PACS No. 63.20.-e, 71.45.Lr, 71.20.Be

Abstract

In a two orbital double exchange model we formulate Jahn-Teller coupled charge density wave in one electron per lattice site limit. Softening of Jahn-Teller phonons corresponding to distortion modes Q_2 or Q_3 associated with perfect nesting of Fermi surface leads to this instability at low temperature. The gap equation for charge density wave state and its dependences on electron-lattice coupling are calculated explicitly when any one of the Jahn-Teller modes is excited cooperatively. We find that the Q_2 distortion mode yields lowest free energy. The calculated heat capacity for each mode shows T^3 behavior at low temperature. Effect of electron-lattice interaction on collective mode, such as amplitude mode, is more pronounced when the excited mode is Q_2.

*e-mail: mmitra@bose.res.in

I. INTRODUCTION

It is widely accepted that the collective nature of coupling of e_g electrons to the underlying lattice degrees of freedom have great impact on extraordinary properties of the colossal magneto resistive (CMR) manganites [1]. The parent compound $LaMnO_3$ contains Jahn-Teller (JT) ions Mn^{3+}, which is orbitally degenerate. The on-site vibrational modes of the MnO_6 octahedra are breathing mode Q_1 and the Jahn-Teller modes – Q_2 (in-plane distortion mode), Q_3 (octahedral stretching mode). Due to the coupling between the e_g electrons and Q_2, Q_3 modes the degeneracy of Mn^{3+} is lifted. In the lattice the MnO_6 octahedra are co-operatively stretched out, resulting a C - type orbital and A - type spin antiferromagnet structure [2]. Several recent experimental investigations such as high-resolution electron microscopy [3], THz time-domain spectroscopy [4], high-resolution ARPES [5], non-linear electrical response [6], x-ray and neutron scattering [7,8] measurements reveal the evidence of charge density waves in different composition of CMR manganites. Moreover, ARPES results [5] show Fermi surface nesting, which ensures the possibility of density wave formation in these materials. It is well known that in a low dimensional one orbital system, due to particular geometry of the Fermi surface, electron-phonon interactions lead to periodic lattice distortions. This results a ground state characterized by a gap in the single particle excitation spectrum at low temperature, which is known as charge density wave (CDW) [9]. In CMR manganites the Jahn-Teller vibrational modes play major role to shape the properties of these systems compared to the breathing mode phonon Q_1 which does not alter the symmetry of the MnO_6 octahedron. The distribution of charge density at two e_g orbitals, $d_{x^2-y^2}$ and $d_{3z^2-r^2}$, depends on excited JT mode. In presence of these two orbitals, the electron can be either in any one of the orbitals or in any linear combination of two [10]. It appears that the perfect nesting of the Fermi surface associated with Jahn-Teller distortions may give rise to possibilities of occurrence of charge density waves in these systems. Therefore, the

resulting charge density wave will be coupled to the orbital order of the system. We denote this density wave as Jahn-Teller coupled charge density wave (JTCCDW).

In the present work, we investigate the formation of Jahn-Teller coupled charge density wave instability in two orbital, double exchange model with one electron per site. The paper is organized as follows. In section II we formulate the Hamiltonian for Jahn-Teller coupled charge density wave in two dimension and calculate the JTCCDW order parameter for different JT vibrational modes. To determine the dominant JT distortion mode, we calculate the free energy and hence heat capacity in the JTCCDW state. In the same spirit of CDW system, the spectral density functions of the ordered ground state are calculated from the amplitude mode response function of JTCCDW state generated due to each JT active mode. The results of our calculations are presented in section III. Lastly, in section IV we make some concluding remarks.

II. FORMALISM

We consider two orbital double exchange model in two dimension, and large Hund's rule coupling limit in which the ground state configuration corresponds to the itinerant spin being parallel to the core spin at each site. If one compares our model with the manganite (e.g. $LaMnO_3$) system the core spins and the itinerant electrons may be identified with the t_{2g}^3 (localized) electrons and the e_g^1 (mobile) electrons of Mn^{3+} ion respectively. The kinetic part of the Hamiltonian in momentum representation is given by

$$H_1 = \sum_k B_k^\dagger \mathbf{T} B_k, \tag{1}$$

where $B_k^\dagger \equiv (d_{1,k}^\dagger,\ d_{2,k}^\dagger)$ with d_1 and d_2 being the e_g - electron annihilation operators in two orthonormal orbitals $d_{x^2-y^2}$ and $d_{3z^2-r^2}$ respectively. The elements of the hopping matrix $\mathbf{T}$ are given by $\mathbf{T}_{1,1} = -1.5\tilde{t}[\cos k_x + \cos k_y]$, $\mathbf{T}_{2,2} = -0.5\tilde{t}[\cos k_x + \cos k_y]$, and $\mathbf{T}_{1,2} = 0.5\sqrt{3}\tilde{t}[\cos k_x - \cos k_y]$. The transfer hopping integral t is modified as

$\tilde{t} = t\ \cos(\frac{\theta}{2})$ because of double exchange interaction [11]. If the t_{2g} spins are assumed classical then θ is the relative angle between two neighbouring spins. Thus, in case of ferromagnetic order (FM) $\tilde{t} = t$. We consider that the A-type spin antiferro order has set in. Due to strong Hund's rule coupling the transport is restricted to spin polarizedelectrons in two dimensions only. So the spin degrees of freedom may be omitted in the Hamiltonian without loss of generality.

The Jahn-Teller coupling parts of the Hamiltonian for Q_2 and Q_3 mode can be written as [10]

$$H_{Q_2} = g \sum_i Q_{2i}(d_{1i}^\dagger d_{2i} + d_{2i}^\dagger d_{1i}), \tag{2}$$

$$H_{Q_3} = g \sum_i Q_{3i}(d_{1i}^\dagger d_{1i} - d_{2i}^\dagger d_{2i}), \tag{3}$$

where g is the electron-JT phonon coupling strength. To diagonalize the kinetic part of the Hamiltonian appearing in equation (1) we introduce the new fermionic operators c_k^1 and c_k^2 as

$$\begin{aligned} c_k^1 &= \sin\frac{\theta_k}{2}\ d_{1,k} + \cos\frac{\theta_k}{2}\ d_{2,k}, \\ c_k^2 &= \cos\frac{\theta_k}{2}\ d_{1,k} - \sin\frac{\theta_k}{2}\ d_{2,k}, \end{aligned} \tag{4}$$

with $\tan\theta_k = \frac{\sqrt{3}(\cos\ k_x - \cos\ k_y)}{(\cos\ k_x + \cos\ k_y)}$. The eigen values of the kinetic energy are given by $\lambda_{n,k} = -\cos k_x - \cos k_y - (-1)^n\sqrt{\cos^2 k_x + \cos^2 k_y - \cos k_x \cos k_y}$ where $n = 1, 2$. The Fermi sea corresponding to $\lambda_{1,k}$ is the intersection of the region $-\pi/2 \leq k_x \leq \pi/2$ with the region $-\pi/2 \leq k_y \leq \pi/2$ and corresponding to $\lambda_{2,k}$ is the union of the region $-\pi/2 \leq k_x \leq \pi/2$ (with all values of k_y allowed) to the region $-\pi/2 \leq k_y \leq \pi/2$ (with all values of k_x allowed). It is evident from the symmetry of the bands that at half-filling $\lambda_{1(2),\vec{k}} = -\lambda_{2(1),(\vec{k}+\vec{Q})}$ for $\vec{Q} = (\pi, \pi)$, which shows a perfect nesting at wave vector $\vec{Q}$.

The lattice instability in low dimensional system is usually driven by the softening of the wave vector $\vec{Q}$ due to electron-phonon (e-ph) interactions, which is called Kohn

anomaly. This is a precursor to the Peierls transition. Peierls instability brings about the formation of the CDW with an accompanying periodic lattice distortion which in turn gives rise to a band gap at the Fermi level driving the system from a conductor to a insulator. In order to find how the JT phonon Q_2 or Q_3 softens to set similar instability, it is needed to calculate the phonon self-energy arising from e-ph interaction for Q_2 or Q_3 mode. The phonon response function is determined by the phonon Green's function given by [12],

$$D_{q,q'}(q,q',\omega) = \frac{\omega_q \ \delta_{-q,q'}}{\pi \left[\omega^2 - \omega_q^2 - \omega_q \Pi(q,q',\omega)\right]}. \tag{5}$$

Here $\Pi(q,\omega)$ is the self-energy acquired by the q -th phonon and ω_q is the bare phonon frequency. The phonon self-energy is given by

$$\Pi(q,\omega) = 4\pi^2 g^2 \chi(q,\omega), \tag{6}$$

where $\chi(q,\omega)$ is the density response function. We denote $\chi(q,\omega)$ as $\chi_2(q,\omega)$ and $\chi_3(q,\omega)$ respectively for Q_2 and Q_3 distorted modes.

The phonon response function for Q_2 and Q_3 mode can be written as [13],

$$\begin{aligned} \chi_2(q,\omega) &= \sum_k \ \langle\langle \ \rho_2(q); \rho_2(-q) \ \rangle\rangle_\omega, \\ \chi_3(q,\omega) &= \sum_k \ \langle\langle \ \rho_3(q); \rho_3(-q) \ \rangle\rangle \ _\omega \end{aligned} \tag{7}$$

where $\rho_2(q) = (d^\dagger_{1,k+q} d_{2k} + d^\dagger_{2,k+q} d_{1k})$ and $\rho_3(q) = (d^\dagger_{1,k+q} d_{1k} - d^\dagger_{2,k+q} d_{2k})$. The renormalized phonon frequency with the wave vector $q = \mid \vec{Q} \mid$ corresponding to the Q_2 or Q_3 mode can be determined from the pole of the phonon Green's function, with the static response functions $\chi_2(\vec{Q},0)$ or $\chi_3(\vec{Q},0)$ respectively. It can be shown [14] that $\chi_2(\vec{Q},0)$ and $\chi_3(\vec{Q},0)$ diverges at $T \to 0$.

The response function $\chi_2(\vec{Q},0)$ diverges faster than $\chi_3(\vec{Q},0)$ [14]. The divergence of the response functions with decreasing temperature indicate the softening of Q_2 and Q_3 vibrational modes and hence a possibility of Fermi surface instability. The

temperature at which the soft mode frequency for Q_2 or Q_3 vanishes is the Jahn-Teller coupled charge density wave transition temperature T_{CDW} corresponding to that mode.

In this report, we formulate the Jahn-Teller coupled charge density wave when either Q_2 or Q_3 mode gets excited cooperatively. For this purpose we use (4) and second quantized form of the phonon modes given by $(b_{\vec{q}}^{2(3)}+b_{-\vec{q}}^{2(3)^\dagger})$ for the wave vector $\vec{q}=\vec{Q}$ in equations (2) and (3). By using canonical transformation [15], we derive the effective electron-electron interaction mediated by e-ph interaction as,

$$H_{Q_2}^{e-e} = -\sum_{kk'} \mid \tilde{g}_{kk'} \mid \sin\theta_{k'} \; (c_{k'+Q}^{1\dagger}c_{k'}^{2} + c_{k'}^{2\dagger}c_{k'+Q}^{1} + c_{k'}^{1\dagger}c_{k'+Q}^{2} + c_{k'+Q}^{2\dagger}c_{k'}^{1}) \times \sin\theta_k \; (c_{k+Q}^{1\dagger}c_{k}^{2} + c_{k}^{2\dagger}c_{k+Q}^{1} + c_{k}^{1\dagger}c_{k+Q}^{2} + c_{k+Q}^{2\dagger}c_{k}^{1}), \tag{8}$$

$$H_{Q_3}^{e-e} = -\sum_{kk'} \mid \tilde{g}_{kk'} \mid \cos\theta_{k'} \; (c_{k'+Q}^{1\dagger}c_{k'}^{2} + c_{k'}^{2\dagger}c_{k'+Q}^{1} + c_{k'}^{1\dagger}c_{k'+Q}^{2} + c_{k'+Q}^{2\dagger}c_{k'}^{1}) \times \cos\theta_k \; (c_{k+Q}^{1\dagger}c_{k}^{2} + c_{k}^{2\dagger}c_{k+Q}^{1} + c_{k}^{1\dagger}c_{k+Q}^{2} + c_{k+Q}^{2\dagger}c_{k}^{1}), \tag{9}$$

where $\tilde{g}_{kk'}$ is considered as average interaction strength and $\tilde{g}_{kk'} = -\mid \tilde{g}_{kk'} \mid$. It is to be mentioned here, while deriving the equations (8), (9) we have considered only terms like $c^{1(2)\dagger}c^{2(1)}$ in the electron-phonon interaction.

Now we write the total Hamiltonian corresponding to Q_2 and Q_3 as,

$$H^{Q_2(Q_3)} = H_1 + H_{e-e}^{Q_2(Q_3)}. \tag{10}$$

In the mean-field approximation, the JTCCDW order parameter (Δ_k) for Q_2 and Q_3 modes are respectively defined as,

$$\Delta_k = \Delta_2(-\sin\theta_k) = -\sum_{k'} \mid \tilde{g}_{kk'} \mid \sin\theta_{k'} \; \sin\theta_k \langle c_{k'+Q}^{1\dagger}c_{k'}^{2} + c_{k'}^{2\dagger}c_{k'+Q}^{1} + c_{k'}^{1\dagger}c_{k'+Q}^{2} + c_{k'+Q}^{2\dagger}c_{k'}^{1}\rangle, \tag{11}$$

$$\Delta_k = \Delta_3\cos\theta_k = -\sum_{k'} \mid \tilde{g}_{kk'} \mid \cos\theta_{k'} \; \cos\theta_k \langle c_{k'+Q}^{1\dagger}c_{k'}^{2} + c_{k'}^{2\dagger}c_{k'+Q}^{1} + c_{k'}^{1\dagger}c_{k'+Q}^{2} + c_{k'+Q}^{2\dagger}c_{k'}^{1}\rangle, \tag{12}$$

where $\Delta_2(\Delta_3)$ is the amplitude of the JTCCDW gap generated due to $Q_2(Q_3)$ mode. Therefore, the JTCCDW Hamiltonian can be obtained from (10) as

$$H_{JTCCDW}^{Q_2(Q_3)} = \sum_k \lambda_{1,k}(c_k^{1\dagger}c_k^1 - c_{k+Q}^{2\dagger}c_{k+Q}^2) + \sum_k \lambda_{2,k}(c_k^{2\dagger}c_k^2 - c_{k+Q}^{1\dagger}c_{k+Q}^1) + \sum_k \Delta_k(c_{k+Q}^{1\dagger}c_k^2 + c_k^{2\dagger}c_{k+Q}^1 + c_k^{1\dagger}c_{k+Q}^2 + c_{k+Q}^{2\dagger}c_k^1), \tag{13}$$

while Δ_k is different for Q_2 and Q_3 mode according to equations (11) and (12). To diagonalize the Hamiltonian $H_{JTCCDW}^{Q_2(Q_3)}$ we use the following two simultaneous canonical transformations :

$$\begin{aligned} \alpha_{1,k} &= \sin\frac{\phi_k}{2}\ c_k^1 + \cos\frac{\phi_k}{2}\ c_{k+Q}^2, \\ \beta_{1,k} &= \cos\frac{\phi_k}{2}\ c_k^1 - \sin\frac{\phi_k}{2}\ c_{k+Q}^2, \end{aligned} \tag{14}$$

where $\cos(\frac{\phi_k}{2}) = \frac{1}{\sqrt{2}}\left(1 - \frac{\lambda_{1,k}}{\sqrt{\lambda_{1,k}^2+\Delta_k^2}}\right)^{\frac{1}{2}}$, $\sin(\frac{\phi_k}{2}) = \frac{1}{\sqrt{2}}\left(1 + \frac{\lambda_{1,k}}{\sqrt{\lambda_{1,k}^2+\Delta_k^2}}\right)^{\frac{1}{2}}$ and

$$\begin{aligned} \alpha_{2,k} &= \sin\frac{\delta_k}{2}\ c_k^2 + \cos\frac{\delta_k}{2}\ c_{k+Q}^1, \\ \beta_{2,k} &= \cos\frac{\delta_k}{2}\ c_k^2 - \sin\frac{\delta_k}{2}\ c_{k+Q}^1, \end{aligned} \tag{15}$$

with $\cos(\frac{\delta_k}{2}) = \frac{1}{\sqrt{2}}\left(1 - \frac{\lambda_{2,k}}{\sqrt{\lambda_{2,k}^2+\Delta_k^2}}\right)^{\frac{1}{2}}$ and $\sin(\frac{\delta_k}{2}) = \frac{1}{\sqrt{2}}\left(1 + \frac{\lambda_{2,k}}{\sqrt{\lambda_{2,k}^2+\Delta_k^2}}\right)^{\frac{1}{2}}$. These transformations yield the quasi particle energies as $E_k^{\alpha_1} = -E_k^{\beta_1} = \sqrt{(\lambda_{1,k}^2 + \Delta_k^2)}$ and $E_k^{\alpha_2} = -E_k^{\beta_2} = \sqrt{(\lambda_{2,k}^2 + \Delta_k^2)}$, which correspond to resulting four bands α_1, β_1, α_2 and β_2 respectively. The diagonalized Hamiltonian in presence of either Q_2 or Q_3 mode can now be written as,

$$H_{JTCCDW}^{Q_2(Q_3)} = \left[E_k^{\alpha_1}(\alpha_{1,k}^\dagger\alpha_{1,k} - \beta_{1,k}^\dagger\beta_{1,k}) + E_k^{\alpha_2}(\alpha_{2,k}^\dagger\alpha_{2,k} - \beta_{2,k}^\dagger\beta_{2,k})\right]. \tag{16}$$

The gap equations can be written for Q_2 mode as

$$1 = \tilde{g}\sum_k \sin^2\theta_k\ \left[\frac{\tanh\ (\beta\ E_k^{\alpha_1}/2)}{E_k^{\alpha_1}} + \frac{\tanh\ (\beta\ E_k^{\alpha_2}/2)}{E_k^{\alpha_2}}\right], \tag{17}$$

and for the Q_3 mode as

$$1 = \tilde{g}\sum_k \cos^2\theta_k\ \left[\frac{\tanh\ (\beta\ E_k^{\alpha_1}/2)}{E_k^{\alpha_1}} + \frac{\tanh\ (\beta\ E_k^{\alpha_2}/2)}{E_k^{\alpha_2}}\right], \tag{18}$$

where for simplicity we have taken $\mid \tilde{g}_{kk'} \mid = \tilde{g}$. It is clear that both the amplitudes Δ_2 and Δ_3 are symmetric in k_x and k_y sector of the Fermi surface, but Δ_k are highly anisotropic in k-space. The effective temperature, $\widetilde{T} = k_B T t$ enters in (17) and (18) through $\beta = 1/(k_B T t)$. The free energy of the system can then be calculated as

$$F = -\frac{1}{\beta} \sum_{k,i} \ln(1 + e^{-\beta E_k^i}), \tag{19}$$

where $E_k^i = E_k^{\alpha_1}$, $E_k^{\beta_1}$, $E_k^{\alpha_2}$, $E_k^{\beta_2}$. Hence the heat capacity can also be calculated from the relation,

$$C_V = -\ \widetilde{T}\ \frac{d^2 F}{d\widetilde{T}^2}. \tag{20}$$

We like to point out here that the four band Hamiltonian, similar to equation (16), is also obtained by Jackeli et al [16] considering only nearest neighbor Coulomb correlation in a double degenerate system. To explain the nontrivial observed order in $LaMnO_3$, several studies have been reported based on either purely Coulombic interaction or Jahn-Teller interaction [1]. In the framework of two orbital model, purely Coulombic approaches produce correct spin ordered (A-type spin antiferromagnetic) state [17,18], while giving conflicting results regarding the orbital order that co-exists with the A-type spin state. According to Hotta et al [19], Jahn-Teller based calculations lead to experimentally observed A-type spin and C-type orbital order in a model for undoped manganites. Therefore, in the present calculation focussing on undoped manganites, we formulate our model based on the Jahn-Teller coupling.

The robustness of the ordered ground state is usually tested by looking at the response of the system to small fluctuations. In case of CDW state, it is well known that fluctuations of the phase and the amplitude of the order parameter results in the appearance of the collective modes of the system [9]. The amplitude mode is a measure of the CDW order parameter. In the present work, we want to calculate the spectral density function for the JTCCDW state, from the amplitude response function $\chi^a_{2,3}(q, \tilde{\omega})$ for the Q_2 or Q_3 modes. The amplitude response function is given by,

$$\chi^a_{2,3}(q,\omega) = \sum_{k,k'} f(\theta_{(k+q)},\theta_{(k'+q)})$$
$$\langle\langle\ (\sum_{i=1,2}\Psi^\dagger_{ik}(t)\hat{\tau}_1\Psi_{ik+q}(t)); (\sum_{i=1,2}\Psi^\dagger_{ik'+q}(0)\hat{\tau}_1\Psi_{ik'}(0))\ \rangle\rangle_{\ \tilde{\omega}}, \tag{21}$$

where

$$f(\theta_k,\theta_{k'}) = \sin\theta_k\ \sin\theta_{k'}; \qquad for\ Q_2 - mode$$
$$= \cos\theta_k\ \cos\theta_{k'}; \qquad for\ Q_3 - mode, \tag{22}$$

and $\Psi^\dagger_{1,(2)\ k} \equiv (c^{1,(2)\ \dagger}_k\ \ c^{2,(1)\ \dagger}_{k+Q})$, are similar to Nambu operators. $\hat{\tau}_1$ is the Pauli matrix. Within the random phase approximation (RPA), we obtain,

$$\chi^a_{2,3\ RPA}(q,\tilde{\omega}) = \frac{\chi^a_{2,3}(q,\tilde{\omega})}{\left[1-\tilde{g}\chi^a_{2,3}(q,\tilde{\omega})\right]}. \tag{23}$$

The spectral density function is related to imaginary part of $\chi_{RPA}(\tilde{\omega})$, which is given by,

$$S\ (0,\ \tilde{\omega})\ =\ Im\ \chi^a_{2,3\ RPA}(\tilde{\omega}) = \frac{\chi^I_{2,3}(0,\tilde{\omega})}{(1-\tilde{g}\chi^R_{2,3}(0,\tilde{\omega}))^2 + (\tilde{g}\chi^I_{2,3}(0,\tilde{\omega}))^2}, \tag{24}$$

where $\chi^R_{2,3}(0,\tilde{\omega})$ and $\chi^I_{2,3}(0,\tilde{\omega})$ are respectively the real and imaginary part of $\chi^a_{2,3}(0,\tilde{\omega})$. By using equation (21) the expressions for $\chi^a_{2,3}(0,\tilde{\omega})$ are obtained as,

$$\chi^a_2(0,\tilde{\omega}) = 4\sin^2\theta_k\ \ \chi(Q,\tilde{\omega})$$
$$\chi^a_3(0,\tilde{\omega}) = 4\cos^2\theta_k\ \ \chi(Q,\tilde{\omega}), \tag{25}$$

with

$$\chi(Q,\tilde{\omega}) = \sum_k \left[\cos^2\phi_k\ \frac{E^{\alpha_1}_k\tanh\ (\beta E^{\alpha_1}_k/2)}{\tilde{\omega}^2\ -\ 4{E^{\alpha_1}_k}^2} + \cos^2\delta_k\ \frac{E^{\alpha_2}_k\tanh\ (\beta E^{\alpha_2}_k/2)}{\tilde{\omega}^2\ -\ 4{E^{\alpha_2}_k}^2}\right]. \tag{26}$$

III. RESULTS AND DISCUSSIONS

In previous section we have formulated a theory for the charge density wave state in a Jahn-Teller active system. Self consistent solution of equation (17) or (18) yields

Δ_2 or Δ_3 respectively. All parameters are expressed in units of t however temperature T is expressed as $\widetilde{T} = k_B T t$. In figure 1, we show the variation of Δ_2 and Δ_3 (in units of t) with temperature $\widetilde{T}$ in a FM spin state. It is evident that the magnitude of JTCCDW gap decreases with increasing temperature. The magnitude as well as transition temperature $\widetilde{T}_{CDW}$ for Q_3 mode is larger than that of Q_2 mode for $\widetilde{g} = 1$. The magnitude of Δ_3 is not always larger than Δ_2. This is depicted in figure 2, where variation of JTCCDW gap with $\widetilde{g}$ is shown for a very low temperature. It is shown in figure 2 that Q_2 distortion mode opens up JTCCDW gap at a lower value of $\widetilde{g}$ than that due to Q_3 mode and Δ_3 is less than Δ_2 till $\widetilde{g} \leq 0.6$. With increasing value of $\widetilde{g}$ both Δ_2 and Δ_3 increases and for values of $\widetilde{g}$ greater than 0.6, Δ_2 is less than Δ_3. So it is clear that the JT modes have different electron-phonon interaction dependences. To determine the dominant JT mode we show the variation of free energy F in FM state, with $\widetilde{g}$ in figure 3. At very small values of $\widetilde{g}$, e-ph coupling does not alter the energy significantly, hence presence of either of the JT modes yields the same energy. For higher values of $\widetilde{g}$ the JT coupling becomes pronounced and it is evident from figure 3 that Q_2 distortion mode acquires lowest free energy for any value of $\widetilde{g}$.

It is well known that low temperature heat capacity (C_V) of CMR manganites has a bearing on many fundamental properties like density of states, lattice contribution and spin wave stiffness. Recent experiments on insulating $LaMnO_3$ [20] show that at low temperature, C_V/T vs T^2 plot gives approximately straight lines. In an attempt to compare the lattice contributions of the specific heat in JTCCDW state driven by Q_2 or Q_3 mode, we show a plot of $C_V/\widetilde{T}$ vs $\widetilde{T}^2$ in figure 4 at low temperature. Figure 4 shows that at low temperature the T^3 behavior is pronounced for both the JT modes but the Debye temperatures seem to be different.

Very recently in Raman scattering experiment on $LaMnO_3$ [21] by Saitoh et al, the orbital excitations were observed. According to Brink [22], the elementary excitations of $LaMnO_3$ show both the orbital and phonon character due to the mixing of orbital

and phonon modes. In the present system, JTCCDW state occurs due to softening of either Q_2 mode or Q_3 mode. Here charge densities at different e_g orbitals depend on whether Q_2 or Q_3 phonon coupling is active. The Q_3 mode couples with the electron density difference of $d_{x^2-y^2}$ and $d_{3z^2-r^2}$ orbitals whereas the Q_2 mode interacts with the charge density difference between bonding and anti bonding orbitals formed by these two orbitals [14]. It is expected that the low lying collective excitations of resulting JTCCDW will show different $\widetilde{g}$ dependence for Q_2 and Q_3 modes. It is evident from equation (24), (25) and (26) that spectral density function $S(0,\widetilde{\omega})$ for amplitude mode at some symmetry points are due to any one of the JT modes. As example, all spectral density at symmetry point (0, 0) is due to Q_3 mode while at (π, 0) only Q_2 mode contributes to $S(0,\widetilde{\omega})$. It is also obvious that at these symmetry points the CDW gap exists due to the JT mode which contributes to $S(0,\widetilde{\omega})$. However, the $S(0,\widetilde{\omega})$ as well as Δ_k at (π, $\pi/2$) is finite for both Q_2 and Q_3 mode. In figure 5 and figure 6 we show $S(0,\widetilde{\omega})$ at (π, $\pi/2$) for different values of $\widetilde{g}$ in Q_2 and Q_3 excited CDW state respectively. With increasing $\widetilde{g}$ the peak shifts to higher values of frequency $\widetilde{\omega}$ for both the JT modes, because the amplitude of the JTCCDW gap increases for both the modes. It is important to note that the peak position of $S(0,\widetilde{\omega})$ shifts more for Q_2 mode than that of Q_3 with equal increase of $\widetilde{g}$. So the electron lattice interaction has more pronounced effect on the collective excitations of Q_2 active CDW state than that of Q_3 mode.

IV. CONCLUSIONS

The charge density wave may have its origin due to softening of the breathing mode phonon or Jahn-Teller phonons. Emergence of the Jahn-Teller coupled charge density wave is relevant in a system where Jahn-Teller phonons play a crucial role to determine the orbital ordering. In the limit of one electron per site and strong Hund's rule coupling, we provide a comprehensive study of the formation of charge density

wave emphasizing on e_g electron - Jahn-Teller coupling in a orbital ordered system with two kinds of orbitals alternating on adjacent sites in the $x-y$ plane. The in-plane distortion mode – Q_2 is the dominant mode and it opens up JTCCDW gap at smaller electron-lattice interaction strength than the octahedral stretching mode – Q_3. The heat capacity shows T^3 behavior at low temperature. At some of the k-points, the effect of the electron-lattice interaction on collective mode such as amplitude mode is more pronounced when the excited Jahn-Teller mode is Q_2.

The present calculation is done for a system with one electron per lattice site and either of the JT modes is active. The divergence of the phonon response functions corresponding to Q_2 or Q_3 mode ensures their softening and hence the formation of CDW state. However, in presence of both the modes, as in real systems, it is complicated to formulate the charge density wave instability from first principle calculation. With hole doping in the present system there will be decrease of Jahn-Teller active Mn^{3+} ions and the perfect nesting of the Fermi surface will be destroyed. These are expected to reduce the effective electron-JT interaction as well as JTCCDW gap Δ_k, which may yield a orbitally disordered system. The work along these lines are in progress.

Acknowledgements

This work is supported by SERC, DST, GOVT of India through the Fast Track Scheme for Young Scientists (Project Ref. No. SR/FTP/PS-29/2003). I would like to thank Prof. S. Yarlagadda of Saha Institute of Nuclear Physics, Kolkata for many useful discussions.

REFERENCES

[1] For a review, Y. Tokura, Ed., *Colossal Magnetoresistive Oxides*, (Gordon and Breach, New York, 2000).

[2] Y. Murakami, J. P. Hill, D. Gibbs, M. Blume, I. Koyama, M. Tanaka, H. Kawata, T. Arima, Y, Tokura, K. Hirota and Y. Endoh, Phys. Rev. Lett., **81** , 582 (1998).

[3] T. Nagai, T. Kimura, A. Yamazaki, K. Kimoto, Y. Yokura and Y. Matsui, Phys. Rev. B **68**, 092405 (2003).

[4] Noriaki Kida and Masayoshi Tonouchi, Phys. Rev. B **66**, 024401 (2002).

[5] Y. -D. Chuang, A. D. Gromko, D. S. Dessau, T. Kimura, Y. Tokura, Science **292**, 1509 (2001).

[6] A. Wahl, S. Mercone, A. Pautrat, M. Pollet, Ch. Simon and D. Sedmidubsky, Phys. Rev. B **68**, 094429 (2003).

[7] D. N. Argyriou, H. N. Bordallo, B. J. Campbell, A. K. Cheetham, D. E. Cox, J. S. Gardner, K. Hanif, A. dos Santos, G. F. Strouse, Phys. Rev. B **61**, 15269 (2000).

[8] B. J. Campbell, R. Osborn, D. N. Argyriou, L. Vasiliu-Doloc, J. F. Mitchell, S. K. Sinha, U. Ruett, C. D. Ling, Z. Islam and J. W. Lynn, Phys. Rev. B **65**, 014427 (2002).

[9] G. Grüner, Rev. Mod. Phys. **60**, 1129 (1988).

[10] Phillip B. Allen and Vasili Perebeinos, Phys. Rev. B**60**, 10747 (1999).

[11] P. W. Anderson and H. Hasegawa, Phys. Rev. **100**, 675 (1955).

[12] G. D. Mahan, *Many Particle Physics*, (Plenum Press, New York, 1981).

[13] Sudhakar Yarlagadda, Int. Jr. Mod. Phys., **27**, 3529 (2001).

[14] Sudhakar Yarlagadda and Manidipa Mitra, cond-mat/0310350.

[15] C. Kittel, *Quantum Theory of Solids*, (John Wiley and Sons. Inc., New York, 1987).

[16] G. Jackeli, N. B. Perkins and N. M. Plakida, Phys. Rev. B **62**, 372(2000).

[17] R. Maezono, S. Ishihara and N. Nagaosa, Phys. Rev B **57**, R13 993 (1998).

[18] L. F. Feiner and A. M. Oleś, Phys. Rev. B bf 59, 3295(1999).

[19] T. Hotta, S. Yunoki, M. Mayr and E. Dagotto, Phys. Rev. B **60**, R15 009 (1999).

[20] L. Ghivelder, I. Abrego Castillo, M. A. Gusmão, J. A. Alonso, L. F. Cohen, Phys. Rev. B**60**, 12184 (1999).

[21] E. Saitoh, S. Okamoto, K. T. Takahashi, K. Kobe, K. Yamamoto, T. Kimura, S. Ishihara, S. Maekawa and Y. Tokura, Nature(London) **410**, 180 (2001).

[22] Jeroen van den Brink, Phys. Rev. Lett. **87**, 217202 (2001).

Figure captions :

Fig. 1. Thermal variations of the Δ_2 (solid line) and Δ_3 (dashed line) in FM state, for $\widetilde{g} = 1.0$. Here, $\widetilde{T} = k_B T t$.

Fig. 2. Variations of Δ_2 (solid line) and Δ_3 (dashed line) with $\widetilde{g}$ at $\widetilde{T} = (k_B T t) = 10^{-5}$ in FM state.

Fig. 3. Variation of free energy F in **FM** state for Q_2 distorted CDW state (solid line) and Q_3 distorted CDW state (dashed line) with $\widetilde{g}$ at $\widetilde{T} = 0.005$.

Fig. 4. $C_V/\widetilde{T}$ vs $\widetilde{T}^2$ plot in FM state for Q_2 active (solid line) and Q_3 active (dashed line) CDW state with $\widetilde{g} = 1.0$. Here C_V is in arbitrary units and $\widetilde{T} = k_B T t$.

Fig. 5. Spectral density functions $S(0, \widetilde{\omega})$, for the JTCCDW amplitude mode as a function of frequency $\widetilde{\omega}$ (in unit of t) in presence of Q_2 distortion, at k-point (π, $\pi/2$), for different values of $\widetilde{g} = 0.45$, 1.0, 1.5.

Fig. 6. Spectral density functions $S(0, \widetilde{\omega})$, for the JTCCDW amplitude mode as a function of frequency $\widetilde{\omega}$ (in unit of t) in presence of Q_3 distortion, at k-point (π, $\pi/2$), for different values of $\widetilde{g} = 0.45$, 1.0, 1.5.

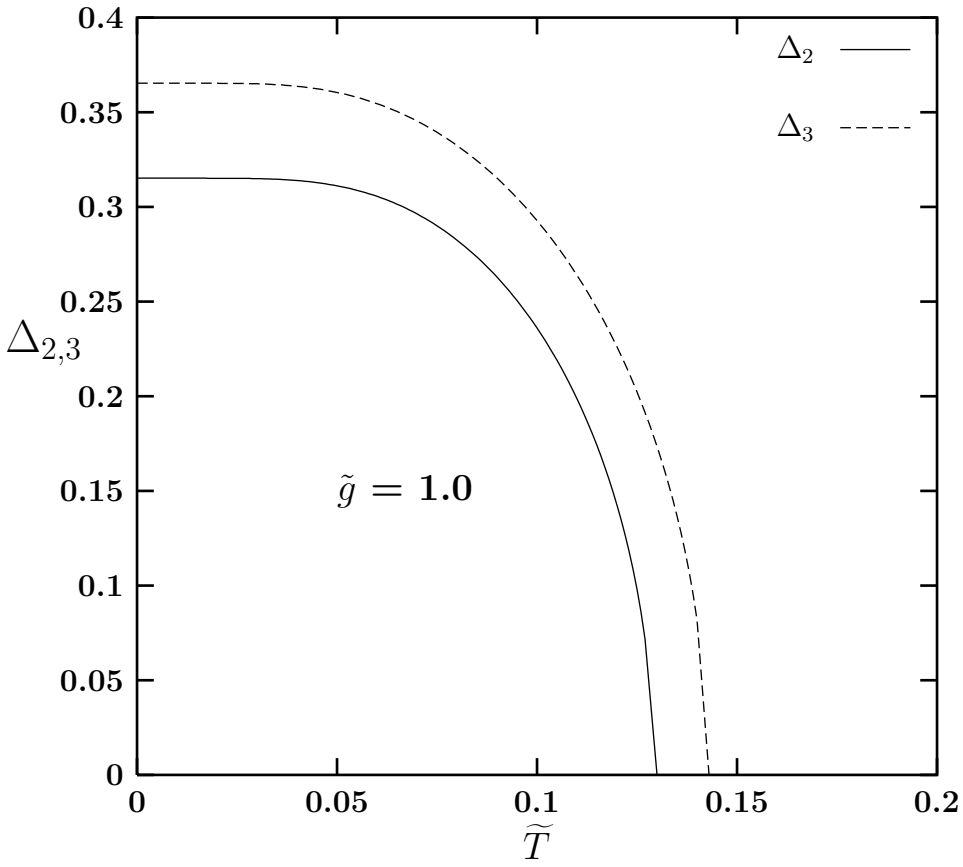
0.4
0.35
0.3
0.25
0.2
0.15
0.1
0.05
0
$\Delta_{2,3}$
Δ_2
Δ_3
$\tilde{g} = 1.0$
0
0.05
0.1
0.15
0.2
$\widetilde{T}$

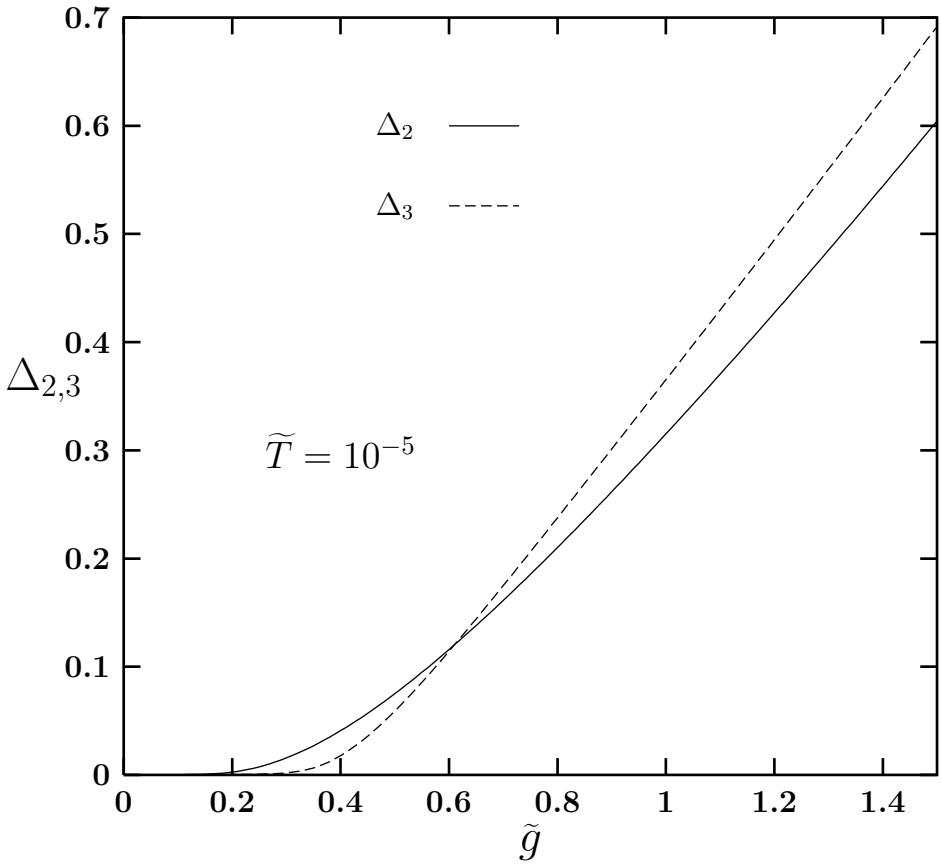
0.7
0.6
0.5
0.4
0.3
0.2
0.1
0
0
0.2
0.4
0.6
0.8
1
1.2
1.4
$\Delta_{2,3}$
$\widetilde{g}$
Δ_2
Δ_3
$\widetilde{T} = 10^{-5}$

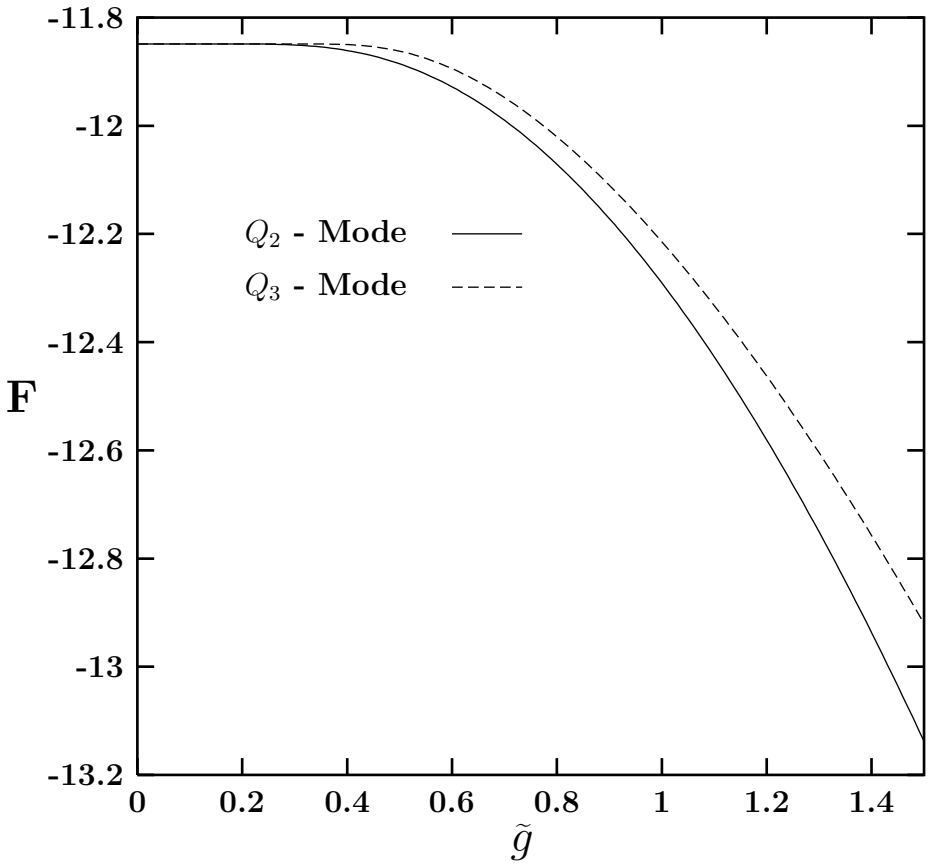
-11.8
-12
-12.2
-12.4
-12.6
-12.8
-13
-13.2
F
0
0.2
0.4
0.6
0.8
1
1.2
1.4
$\tilde{g}$
Q_2 - Mode
Q_3 - Mode

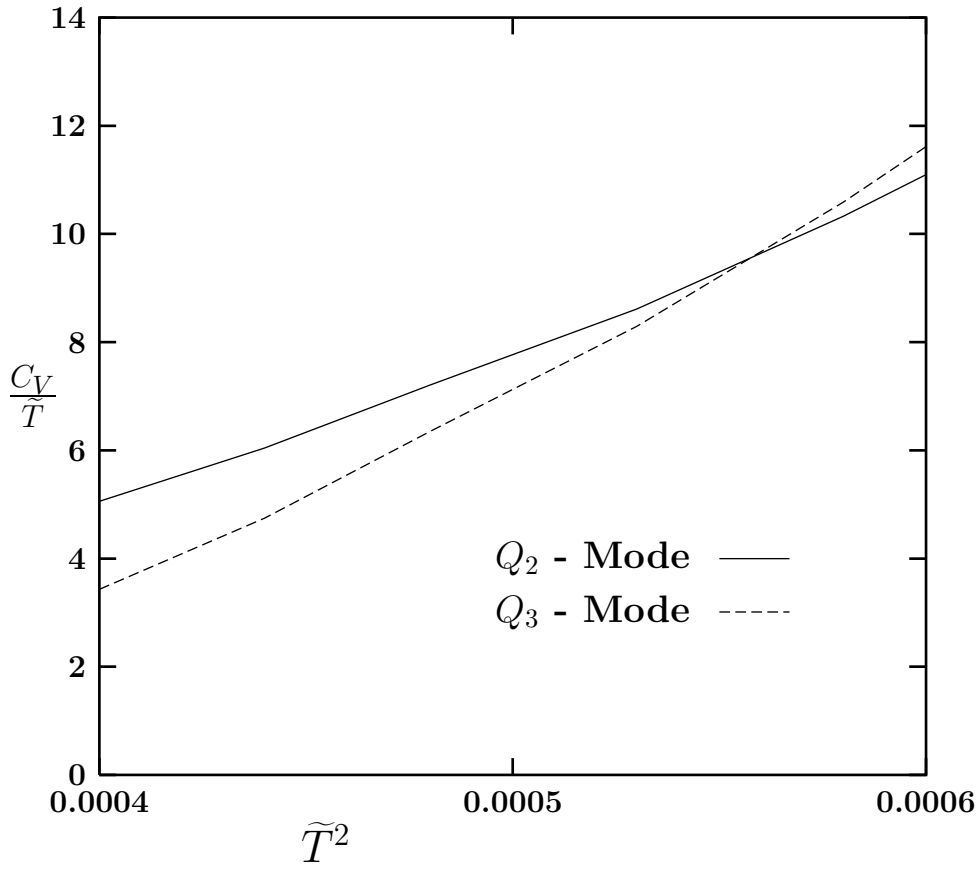
14
12
10
8
6
4
2
0
$\frac{C_V}{\widetilde{T}}$
0.0004
0.0005
0.0006
$\widetilde{T}^2$
Q_2 - Mode
Q_3 - Mode

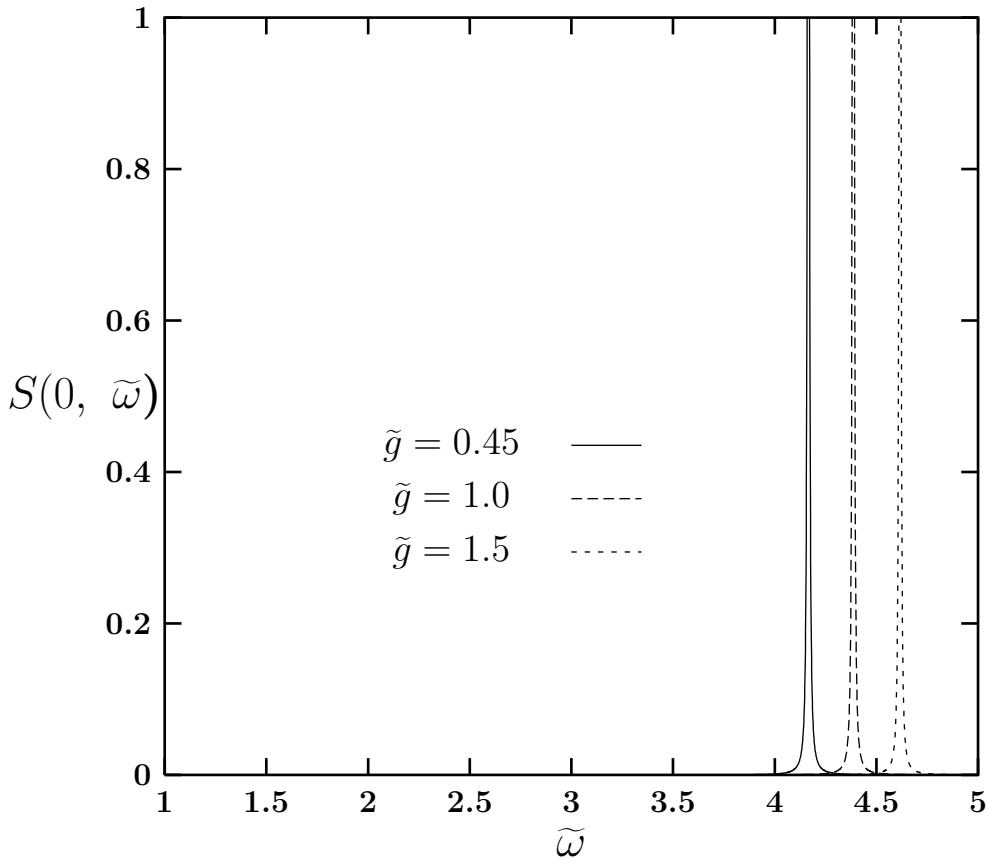
1
0.8
0.6
0.4
0.2
0
1
1.5
2
2.5
3
3.5
4
4.5
5
$S(0,\ \widetilde{\omega})$
$\widetilde{\omega}$
$\widetilde{g} = 0.45$
$\widetilde{g} = 1.0$
$\widetilde{g} = 1.5$

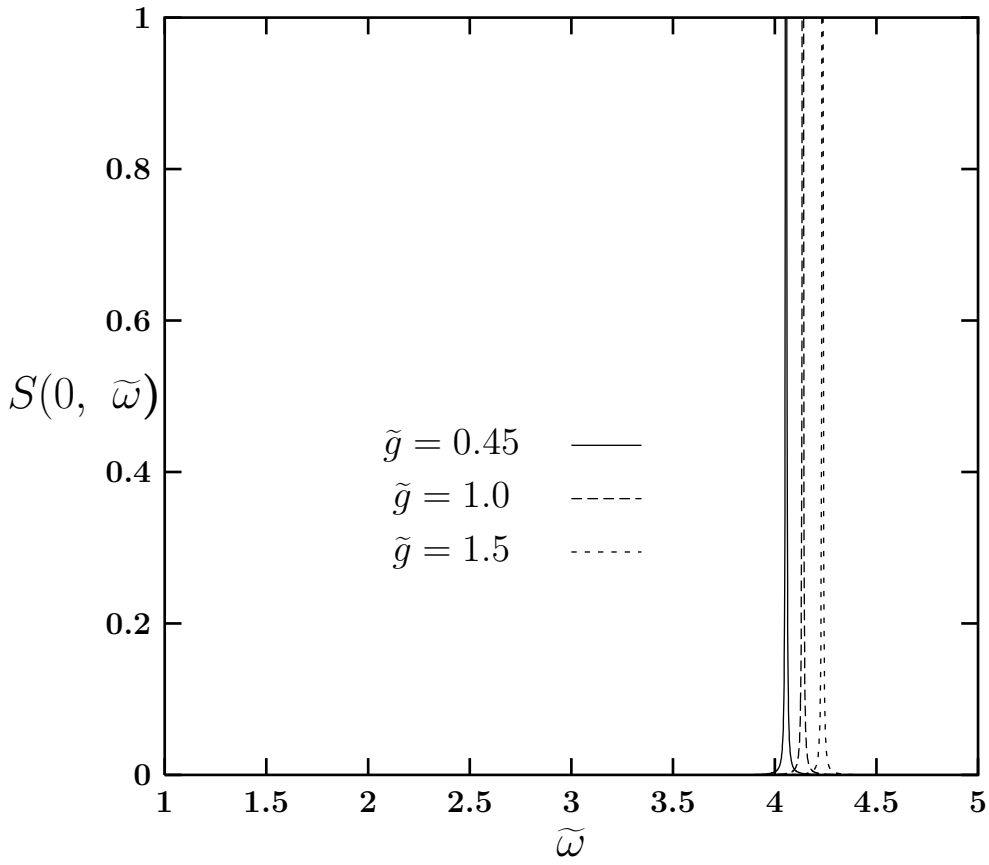
1
0.8
0.6
0.4
0.2
0
1
1.5
2
2.5
3
3.5
4
4.5
5
$S(0,\ \widetilde{\omega})$
$\widetilde{\omega}$
$\widetilde{g} = 0.45$
$\widetilde{g} = 1.0$
$\widetilde{g} = 1.5$